

Soot Oxidation in Diesel Exhaust on Silver Catalyst Supported by Alumina, Titanium and Zirconium

Punya Promhuad^{1,2,*} and Boonlue Sawatmongkhon^{1,2}

¹College of Industrial Technology, King Mongkut's University of Technology North Bangkok, 1518 Pracharat 1 Road, Wongsawang, Bangsue, Bangkok 10800, Thailand.

²Research Centre for Combustion Technology and Alternative Energy (CTAE), Science and Technology Research Institute, King Mongkut's University of Technology North Bangkok, Thailand.

Abstract. Diesel Particulate Filter (DPF) is used to limit the emission of particulate matter (PM). The operation of DPF has two consecutive functions which are filtration of PM and regeneration. Performance of DPF is reduced by clogging of the filter. This problem is improved by soot oxidation in the regeneration process. The soot is completely oxidized by oxygen when temperature is higher than 600 °C. However, the exhaust gas temperature in normal operating of the diesel engine is lower than the temperature of soot complete oxidation. The problem of low temperature in soot oxidation is improved by oxidation catalyst because the oxidation catalyst is used to reduce light of temperature in soot oxidation. The study's purpose is to compare the oxidation activity of silver catalyst supported on alumina (Al₂O₃), Titanium oxide (TiO₂), and Zirconium oxide (ZrO₂). The compression of soot oxidation on silver catalyst loaded on several support which showed silver base on alumina was the best of soot oxidation compared with titanium oxide and zirconium oxide. The behaviour of soot oxidation in silver base on titanium oxide and zirconium oxide were similar activity.

Keyword. Soot oxidation, Silver catalyst, TiO₂, ZrO₂

1 Introduction

Air pollution from the emissions of diesel vehicles, such as particulate matter (PM) and nitrogen oxides (NO_x), has been caused harm to human health [1]. There are many technologies to reduce the pollution such as using the biodiesel as fuel in diesel engine, and installation of exhaust gas after-treatment system. The diesel engine used biodiesel as fuel that it showed low emission such as hydrocarbon, carbon monoxide, smoke[2]. Currently, diesel particulate filter (DPF) is the device used to control effectively PM emissions[1, 3-4]. The operating of DPF consists of two sequential processes, which are trapping of soot and regeneration. First, the trapping of soot is the process of soot to deposit in porous walls of DPF [3]. Next, the regeneration of DPF is required to reduce the problem of DPF blockages. In normal, soot is oxidized by oxygen at a temperature higher than 600 °C [5-7], which is over the exhaust gas temperature in diesel engine.

The oxidation of soot was promoted using an oxidation catalyst, which assisted to burn soot at lower than temperatures of exhaust gas in diesel engine. Noble-metal (such as Ag, Au, Pd, Ru, and Pt etc.) were used as the active metal in oxidation catalyst [8-9]. Silver was interested as the oxidation catalyst because it prompted active oxygen species [10-12] and showed high stability [3]. Moreover, silver is cheaper than other noble metals (e.g., Pt) [13]. The oxygen species or active oxygen may be classified in to peroxide (O⁻) and

superoxide (O²⁻). The active oxygen transfer to soot which was considered to be an important for soot oxidation activity [4, 14].

Soot oxidation activity was promoted by not only the active metal but also the support materials, such as, Al₂O₃, TiO₂, ZrO₂, and CeO₂. Alumina was widely used as the support material of oxidation catalysts, such as, Pt/Al₂O₃ [15] and Ag/Al₂O₃ [3, 12]. Silver catalyst 16 wt% coated on alumina showed best soot oxidation [3]. The Ag/ZrO₂ showed a promising candidate for oxidizing soot with O₂ when the mole fraction of adding Ag to ZrO₂ was 30 % in citric acid-assisted sol-gel (SG) methods [11]. Moreover, it showed very active catalysts in a fresh or aged state [12]. The titanium oxide, which used with silver catalyst, showed high oxidation efficiency of soot in the tight contact between catalyst and soot [16]. From, several works of literature caused interest in the oxide materials to use with silver metal such as Al₂O₃, TiO₂, and ZrO₂.

The thermogravimetric (TG) methods was used to determine kinetics parameter such as activation energy (E_a) and frequency factor (f(α)) etc. Normally, the activation energy is important kinetic parameter to explain the reaction process and identify the reaction mechanism [17]. The reaction rate of a heterogeneous reaction The Arrhenius equation, which depends on temperature, was used to describe the rate of soot oxidation [18]. The rate of reaction in the case of constant heating rate can be explained by the following equation [19]:

* Corresponding author: s6303026912014@kmutnb.ac.th

$$\frac{d\alpha}{dT} = \frac{A}{\beta} \exp\left(\frac{-Ea}{RT}\right) f(\alpha) \quad (1)$$

when A and Ea are the frequency factor and activation energy, $f(\alpha)$ is the differential conversion function, β is heating rate and R is the universal gas constant. The mass fraction of the soot oxidation decomposition (α) can be calculated by the following equation:

$$\alpha = \frac{m - m_0}{m - m_f} \quad (2)$$

when m is the instantaneous mass of soot, m_0 is the initial mass, and m_f is the final mass. In this work used the Kissinger–Akahira–Sunose to determine activation energy to the following equation[20] :

$$\ln\left(\frac{\beta}{T^{1.92}}\right) = Const - 1.0008\left(\frac{Ea}{RT}\right) \quad (3)$$

The activation energy can be obtained by slope from plot of $\ln(\beta/T^{1.92})$ against $1/T$ for different heating rates at a constant α [20]. From equation (3) can be calculated the activation energy by equation as the following:

$$Ea = \frac{(\text{slope at } \alpha) \times R}{-1.0008} \quad (4)$$

The aim of the following study was to compare the soot oxidation activity of silver catalyst loaded on three metal-oxide supports (e.g., Al_2O_3 , TiO_2 , and ZrO_2) and find the activation energy from soot oxidation. The activity of soot oxidation was used by thermogravimetric (TG) methods in the three heating rates which were 5, 7.5, and 10 °C/min. The activation energy was calculated by KAS method.

2 Experimental

2.1. Catalyst and soot preparation

The silver catalyst used on different supporters was prepared via incipient wetness impregnation that silver nitrate to obtain 16 wt% was dissolved in an appropriate quantity of distilled water [3]. Then, the precursor solution was added dropwise to the powdered supports: γ -alumina, titanium oxide, and zirconium oxide. Then, the solvent was removed by drying at 110 °C for 8 h in an oven. Then, the dry sample will be calcined in static air at 600 °C with a heating rate of 10 °C/min for 2 h.

Soot was directly taken from the exhaust gas of a traditional diesel engine. The engine was operated at a speed of 1000–2000 rpm and load of 25–75% of the maximum load. A stain less steel mesh was rolled at one round and placed inside the exhaust pipe (50 mm ID) then, the trapped soot was collected and dried in a furnace at 110 °C for 8 h [3]. SOF was removed in furnace at 250 °C for 2 h.

2.2 Catalyst activity tests

Catalytic oxidation activity of soot was examined using the TGA method (PerkinElmer® Pyris 1). Soot (10 mg) was physically mixed with the catalyst at the designed weight ratio for 5 min in a stainless steel mortar to obtain the tight contact mode or was shaken for 5 min in a glass tube for the loose contact conditions. Then, the mixture (≈ 10 mg) was sampled and placed in a ceramic crucible and heated from room temperature to 110 °C with a heating rate of 10 °C/min under N_2 and, then, the purge gas was switched to O_2 until temperature 700 with heating rates of 5 °C/min, 7.5 °C/min, and 10 °C/min and the contact of soot on the catalyst is tight contact. Purified oxygen (99.999% purity) with a constant flow rate of 50 cm^3/min was used as the oxidiser. The sample weight was recorded continuously with the change in the temperature. The catalytic activity was assessed by using the following: T_{20} , defined as the onset temperature at which 20% of soot was removed; T_{50} , defined as the temperature at which of soot 50% was completely consumed; T_{90} , defined as the temperature at which 90% of soot oxidation.

3 Result and Discussion

3.1 Diesel soot oxidation

The thermogram profile and its first derivative (DTG) for soot oxidation under the tight contact mode are presented in Fig. 1-3. The x-axis shows the temperature, the y-axis shows the percentage of soot oxidation in figure (a), and the y-axis shows the first derivative of soot oxidation in figure (b). An oxidation reaction was the only interaction of soot (solid carbon) because the SOF was removed in the soot preparation stage. The DTG showed the maximum reaction rate in the oxidation process [3]. In case of pure soot in all the heating rates showed the peak of DTG at 610 °C. It explained the best of oxidation reaction of pure soot at this temperature which confirmed the soot is oxidized by oxygen at a temperature higher than 600 °C[5–7].

In the case of soot used in conjunction with silver supported by alumina. The oxidation of soot was well promoted by Ag/Al_2O_3 as observed from the experimental results from all heating rates. The heating rate was 5 °C/min. The peak of DTG showed the maximum oxidation rate temperature was reduced from 610 °C, in the case of non-catalyst soot, to 353 °C (shows in Fig.1) In case of the heating rate was 7.5 °C/min and 10 °C/min. The result showed similarly the oxidation of soot with case of 5 °C/min. In the case of the heating rate was 7.5 °C/min and 10 °C/min. The result showed similarly the oxidation of soot with a case of 5 °C/min from the peak of DTG at 359 °C and 405 °C in cases 7.5 °C/min and 10 °C/min, respectively (shows in Fig. 2-3).

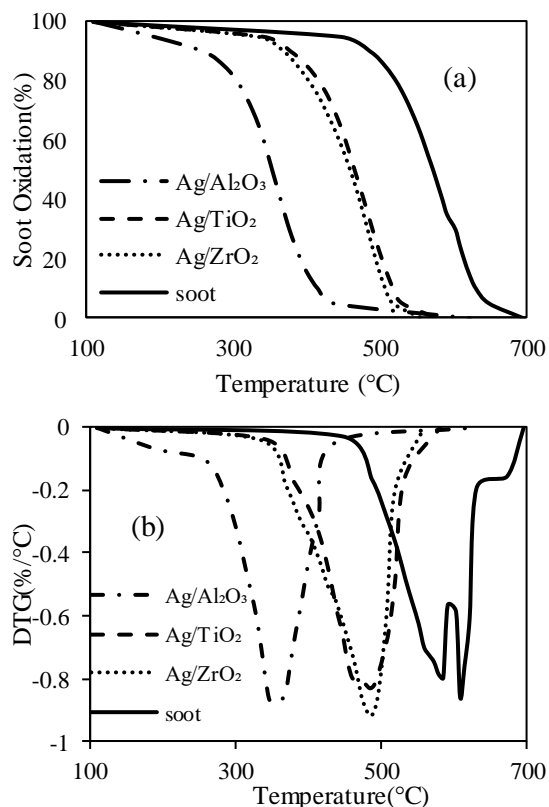


Fig. 1. (a) Thermogravimetric and (b) first derivative profiles of soot oxidation; soot/catalyst weight ratio of 1/5 and heating rate of 5°C/min.

The cases of Ag/TiO₂ and Ag/ZrO₂ showed a similar promotion in soot oxidation due to similar soot oxidation temperatures. Ag/ZrO₂ showed the peak of DTG at temperatures values were 485 °C, 508 °C, and 541 °C for heating rates of 5, 7.5, and 10, respectively (shows in Fig.1-3). Ag/TiO₂ showed the peak of DTG at temperature values were 485 °C, 528°C, and 528 °C for heating rates of 5 °C/min, 7.5°C/min, and 10°C/min, respectively (shows in Fig. 1-3). However, the comparison of Ag/TiO₂ and Ag/ZrO₂ showed that Ag/ZrO₂ had a better-promoting effect on oxidation because the temperature at peak of DTG in the case of Ag/ZrO₂ represented a lower temperature than the case Ag/TiO₂.

Fig.4-6 show T₂₀, T₅₀ and T₉₀ from the experiment had three heating rates which were 5 °C/min, 7.5 °C/min, and 10°C/min. According to Fig.4-6 explained the temperature of percent of soot decomposition since it was oxidized by oxygen. The T₂₀ explained the 20% of soot oxidation. T₂₀ may be indicated as a light of temperature which was the start of soot oxidation. In case of Ag/Al₂O₃ presented excellent to reduce the light of temperature for soot oxidation from 523 °C in case of pure soot was reduced to 305 °C with heating rate 5 °C/min. The results at heating rate 7.5 °C/min and 10 °C/min showed to similar in case of 5 °C/min, they were T₂₀=310 °C and T₂₀ = 342 °C with heating rates of 7.5 °C, and 10°C, respectively. In case of Ag/TiO₂ presented T₂₀ were 417 °C, 438 °C, and 452 °C with heating rates of

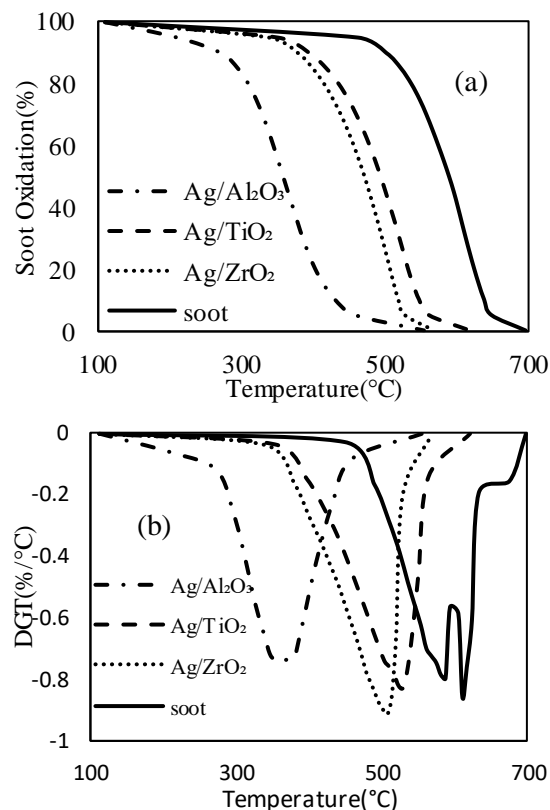


Fig. 2. (a) Thermogravimetric and (b) first derivative profiles of soot oxidation; soot/catalyst weight ratio of 1/5 and heating rate of 7.5°C/min.

5°C/min, 7.5°C/min, and 10 °C/min, respectively. The result from Ag/ZrO₂ showed T₂₀ were 404 °C, 416 °C, and 437 °C with heating rates of 5 °C/min, 7.5°C/min, and 10 °C/min, respectively. The result in several cases in the experiment presented shows light of temperature for soot oxidation as follows: Ag /Al₂O₃< Ag /ZrO₂< Ag /TiO₂< pure soot. It showed the effect of metal oxides supporter to promote soot oxidation because light of temperature for soot oxidation was reduced from pure soot oxidation. In the case of soot oxidation from Ag/TiO₂ and Ag/ZrO₂. The T₂₀ were similar values, it explained the light of soot oxidation which show similar activity in all the heating rates.

The soot oxidation performance was explained by T₅₀ and T₉₀. They were temperature at soot decomposition at 50%(T₅₀) and 90%(T₉₀) from initial mass. The results of T₅₀ in case of Ag/Al₂O₃ was shown in Fig.4-6. The T₅₀ were 353 °C with a heating rate of 5 °C/min. In the case of heating rates were 7 °C/min and 10°C/min that they showed T₅₀ = 359 °C and T₉₀= 398 °C, respectively. The T₉₀ were 353 °C with a heating rate of 5 °C/min, 359 °C with 7 °C/min and 398 °C with 10 °C/min. The results of a silver catalyst supported by alumina showed a good assister to promote soot oxidation. As it reduced the T₅₀ and T₉₀ by half from the case of pure soot. The T₅₀ and T₉₀ in the case of a silver catalyst supported by titanium oxide is shown in Fig.4 - Fig.6.

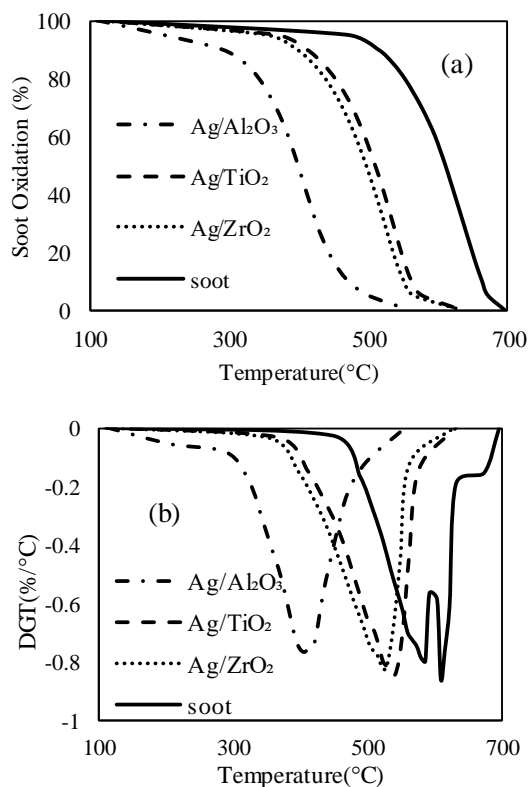


Fig. 3. (a) Thermogravimetric and (b) first derivative profiles of soot oxidation; soot/catalyst weight ratio of 1/5 and heating rate of 10°C/min.

In these cases, the T₅₀ were 466 °C, 495 °C, and 509 °C with heating rates of 5 °C/min, 7.5°C/min, and 10 °C/min, respectively. T₉₀ were 519 °C, 549 °C, and 562 °C with heating rates of 5 °C/min, 7.5°C/min, and 10 °C/min, respectively. In case of silver catalyst supported by zirconium oxide presented T₅₀ = 461 °C with heating rate 5 °C/min, T₅₀ = 473 °C with heating rate 7.5 °C/min, and T₅₀ = 495 °C with heating rate 10 °C/min. The T₉₀ from Ag/ZrO₂ were 519 °C, 549 °C, and 562 °C with heating rates of 5 °C/min, 7.5°C/min, and 10 °C/min, respectively. The results of T₅₀ and T₉₀ from Ag/TiO₂ and Ag/ZrO₂ showed a similar performance to promote soot oxidation. Because T₅₀ and T₉₀ in the case of Ag/ZrO₂ and Ag/TiO₂ were slightly different temperatures. It confirmed the similar activity in soot oxidation. The comparison of soot oxidation performance in several case showed as follows: Ag /Al₂O₃< Ag /ZrO₂< Ag /TiO₂< pure soot. From the results of silver catalyst supported by alumina showed high performance for soot oxidation from the result. Because of it presented to low T₅₀ and T₉₀ which compared with Ag/TiO₂, Ag/ZrO₂, and pure soot in all heating rates.

3.2 Activation energy

The results of the analysis for the determination of Ea used KAS method, it is necessary to find the slope of the plot of ln(β/T^{1.92}) against 1/T for different heating rates at a constant α=0.1 to α=0.9 which showed soot decomposition.

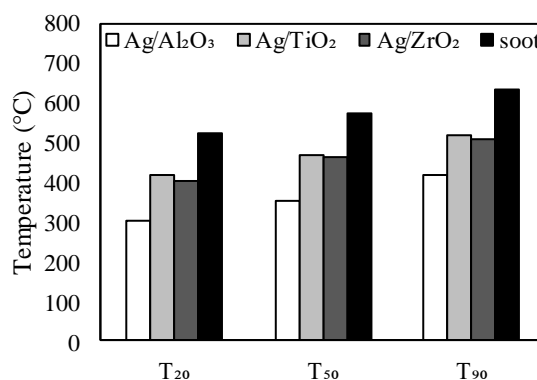


Fig. 4. T₂₀, T₅₀, and T₉₀ of soot oxidation (heating rate 5°C/min)

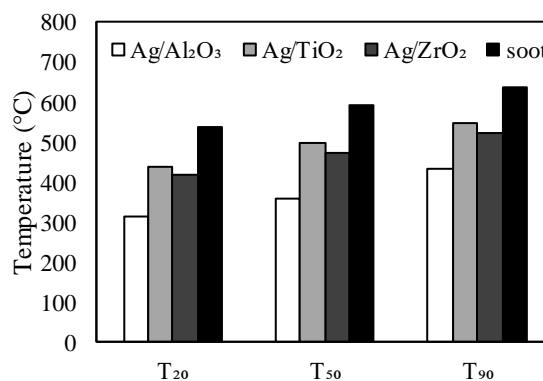


Fig. 5. T₂₀, T₅₀, and T₉₀ of soot oxidation (heating rate 7.5°C/min)

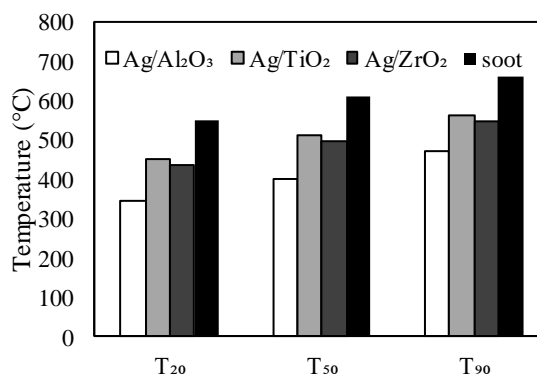


Fig. 6. T₂₀, T₅₀, and T₉₀ of soot oxidation (heating rate 10°C/min)

The case of soot oxidation on the catalyst base on alumina supporter was presented in Fig. 7. it showed α for determine slope of the plot of ln(β/T^{1.92}) against 1/T. From result of calculation in this condition made to activation energy were between 33-49 kJ/mol. Fig.8 and Fig.9 show the plot of ln(β/T^{1.92}) against 1/T and in case of silver catalyst base on titanium oxide can be calculate the activation energy were between 64-79 kJ/mol and case of silver catalyst base on zirconium oxide can be calculate the activation energy were between 71-81 kJ/mol. In case pure soot, the plot of ln(β/T^{1.92}) against 1/T is shown in Fig.10, can be fined the activation energy were between 103-128 kJ/mol. Fig.11 presents the comparison of the activation energy from soot

oxidation in four condition. From results of activation energy were one to explain the performance of soot oxidation. The several cases of silver catalyst base on different metal oxides support showed different activation energy too. This result showed highest of activation energy in pure soot. However, soot loaded on silver catalyst supported by oxide metal. It showed to reduce the activation energy. In the best case of soot oxidation was a silver catalyst supported by alumina because the result of maximum rate oxidation reaction, T_{20} , T_{50} , T_{90} , and activation energy which the most reduced form pure soot oxidation. It attributed alumina well to promote soot oxidation activity. In case of silver catalyst base on titanium oxide and zirconium oxide showed similar of the result to reduce the activation energy, T_{20} , T_{50} , and T_{90} from the oxidation of pure soot.

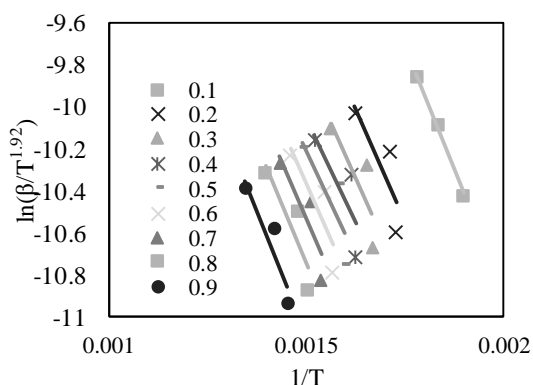


Fig. 7. The plot of $\ln(\beta/T^{1.92})$ against $1/T$ for different heating rates at a constant $\alpha=0.1$ to $\alpha=0.9$ in $\text{Ag}/\text{Al}_2\text{O}_3$.

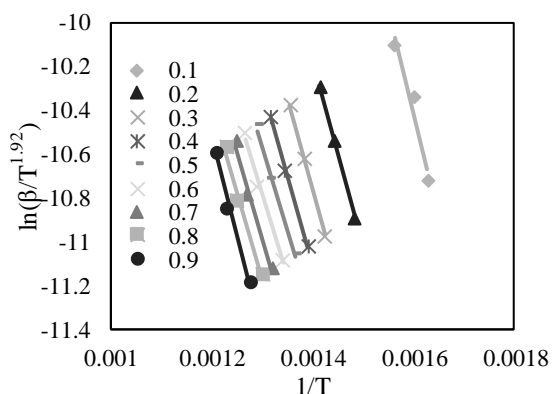


Fig. 8. The plot of $\ln(\beta/T^{1.92})$ against $1/T$ for different heating rates at a constant $\alpha=0.1$ to $\alpha=0.9$ in Ag/TiO_2 .

4 Conclusion

The oxidation activity of silver catalyst supported on alumina (Al_2O_3), titanium oxide (TiO_2), and zirconium oxide (ZrO_2) were tested by the thermogravimetric analysis (TG) to compare soot oxidation performance. The result silver catalyst support by alumina, titanium, and zirconium. It was success to promoted the soot oxidation because the temperature of soot oxidation reaction, maximum of oxidation rate and activation

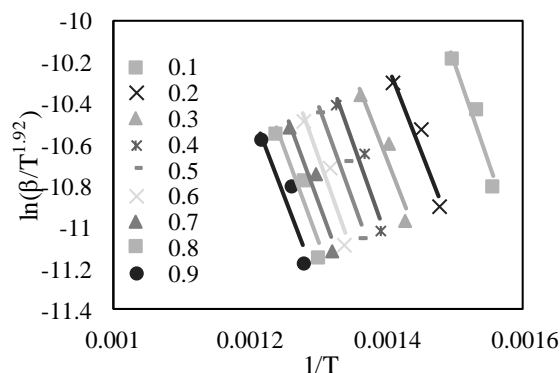


Fig. 9. The plot of $\ln(\beta/T^{1.92})$ against $1/T$ for different heating rates at a constant $\alpha=0.1$ to $\alpha=0.9$ in Ag/ZrO_2 .

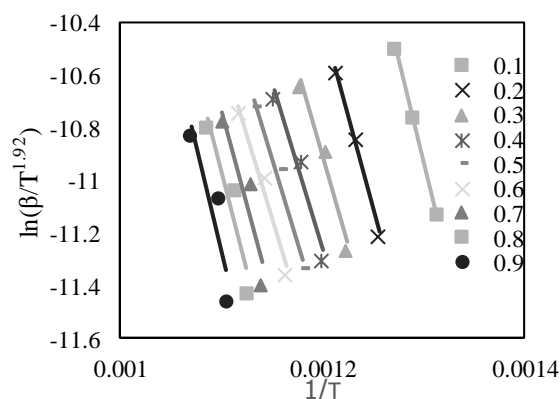


Fig. 10. The plot of $\ln(\beta/T^{1.92})$ against $1/T$ for different heating rates at a constant $\alpha=0.1$ to $\alpha=0.9$ in pure soot.

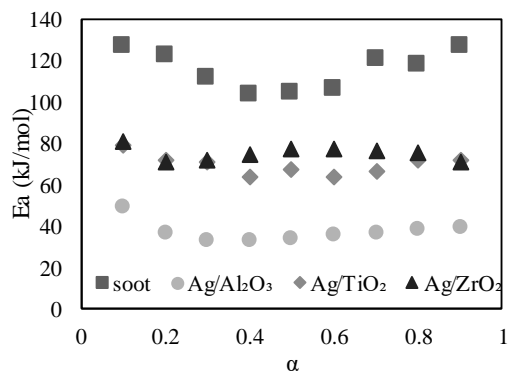


Fig. 11. the comparison of the activation energy from soot oxidation

energy were decrease from temperature in normal soot oxidation. However, the different support in metal oxide group showed the different soot oxidation activity because the activation energy was different which make to different soot oxidation. $\text{Ag}/\text{Al}_2\text{O}_3$ presented $E_a = 33\text{--}49$ kJ/mol, it showed good assister for soot oxidation. Ag/TiO_2 presented $E_a = 64\text{--}79$ kJ/mol and Ag/ZrO_2 presented $E_a = 71\text{--}81$ kJ/mol that the rank of activation energy were similar values, it showed similar of the soot oxidation performance. In future work, the researchers will study the structural characterizations in several catalysts supported by the oxide metal such as specific surface area, crystal structure, and electric state of surface area, etc because some the characteristics of surface properties may assist to promote soot.

Acknowledgement

This research was supported the budget grant from KMUTNB-NSTDA High Performance Post Graduate Scholarship in Science and Technology (KMUTNB-NSTDA HiP Scholarship) and King Mongkut's University of Technology North Bangkok. The researcher would like to show my appreciation in being supported for this research project until it was accomplished very well.

References

1. S. Li *et al.*, Oxidative reactivity enhancement for soot combustion catalysts by co-doping silver and manganese in ceria, *Applied Catalysis A: General.*, **570**, (2019):299–307,
2. S. N. K. Reddy and M. M. Wani, A comprehensive review on effects of nanoparticles-antioxidant additives-biodiesel blends on performance and emissions of diesel engine, *Applied Catalysis A: General.*, **13**, 4(2020): 285–298
3. B. Sawatmongkhon *et al.*, Catalytic oxidation of diesel particulate matter by using silver and ceria supported on alumina as the oxidation catalyst, *Appl. Applied Catalysis A: General.*, **574**, (2020): 33–40
4. K. Krishna, A. Bueno-López, M. Makkee, and J. A. Moulijn, Potential rare earth modified CeO₂ catalysts for soot oxidation. I. Characterisation and catalytic activity with O₂, *Applied Catalysis B: Environmental.*, **75**, 3–4(2007):189–200, 2007,
5. J. Zokoe and P. J. McGinn, Catalytic diesel soot oxidation by hydrothermally stable glass catalysts, *Chemical Engineering Journal*, **262**, (2015): 68–77,
6. R. Matarrese, L. Castoldi, and L. Lietti, Oxidation of model soot by NO₂ and O₂ in the presence of water vapor, *Chemical Engineering Science.*, **173**, 2(2017): 560–569
7. A. Bueno-López, Diesel soot combustion ceria catalysts, *Applied Catalysis B: Environmental.*, **146**, (2014): 1–11
8. T. S. Nguyen, F. Morfin, M. Aouine, F. Bosselet, J. L. Rousset, and L. Piccolo, Trends in the CO oxidation and PROX performances of the platinum-group metals supported on ceria, *Catalysis Today*, **253**, (2015): 106–114
9. M. S. Chen, Y. Cai, Z. Yan, K. K. Gath, S. Axnanda, and D. W. Goodman, Highly active surfaces for CO oxidation on Rh, Pd, and Pt, *Surface Science.*, **601**, 23(2007): 5326–5331
10. K. ichi Shimizu, H. Kawachi, and A. Satsuma, Study of active sites and mechanism for soot oxidation by silver-loaded ceria catalyst, *Applied Catalysis B: Environmental.*, **96**, 1–2(2010): 169–175
11. L. Nossova, G. Caravaggio, M. Couillard, and S. Ntais, Effect of preparation method on the performance of silver-zirconia catalysts for soot oxidation in diesel engine exhaust, *Applied Catalysis B: Environmental.*, **225**, (2018): 538–549
12. E. Aneghi, J. Llorca, C. de Leitenburg, G. Dolcetti, and A. Trovarelli, Soot combustion over silver-supported catalysts, *Applied Catalysis B: Environmental.*, **91**, 1–2(2009): 489–498
13. L. Zeng, L. Cui, C. Wang, W. Guo, and C. Gong, Ag-assisted CeO₂ catalyst for soot oxidation, *Frontiers of Materials Science.*, **13**, 3(2019): 288–295
14. M. Machida, Y. Murata, K. Kishikawa, D. Zhang, and K. Ikeue, On the reasons for high activity of CeO₂ catalyst for soot oxidation, *Chemistry of Materials.*, **20**, 13(2008): 4489–4494
15. C. M. Álvarez-Docio, R. Portela, J. J. Reinoso, F. Rubio-Marcos, and J. F. Fernández, Pt mechanical dispersion on non-porous alumina for soot oxidation, *Catal. Commun.*, **140**, (2020) : 105999
16. M. J. Kim *et al.*, CeO₂ promoted Ag/TiO₂ catalyst for soot oxidation with improved active oxygen generation and delivery abilities, *J. Hazard. Mater.*, **384**, (2020): 121341
17. H. Shimokawa, Y. Kurihara, H. Kusaba, H. Einaga, and Y. Teraoka, Comparison of catalytic performance of Ag- and K-based catalysts for diesel soot combustion, *Catalysis Today*, **185**, 1(2012): 99–103
18. N. Zouaoui, M. Issa, D. Kehrli, and M. Jeguirim, CeO₂ catalytic activity for soot oxidation under NO / O₂ in loose and tight contact, *Catalysis Today*, **189**, 1(2012): 65–69
19. R. López-Fonseca, I. Landa, U. Elizundia, M. A. Gutiérrez-Ortiz, and J. R. González-Velasco, A kinetic study of the combustion of porous synthetic soot, *Chemical Engineering Journal.*, **129**, 1–3(2007): 41–49
20. S. Vyazovkin, A. K. Burnham, J. M. Criado, L. A. Pérez-maqueda, C. Popescu, and N. Sbirrazzuoli, Thermochemical Acta ICTAC Kinetics Committee recommendations for performing kinetic computations on thermal analysis data, *Thermochemical Acta*, **520**, 1–2(2011): 1–19